

1

Introduction

“Where do all these plastic parts actually come from? Who makes them and how are these plastic components even manufactured?” These are questions that hardly anyone asks. “What are those little curls on or in the plastic part, what are they for? Then there is a small spot that looks as if something was cut or torn.” These are all characteristics that are visible on each part and arise in the manufacturing of plastic parts. For this manufacturing technique, besides an injection molding machine and plastic granulates, an injection mold is needed.

Review your day and think about how many plastic parts you held in your hand, and then you can imagine that firstly there is an incredible number of injection molds and secondly the diversity of injection molds there must be in a variety of industries, applications, or life situations.



For each plastic part which is manufactured there is the corresponding injection mold. There are at least as many injection molds as different plastic parts, worldwide. Nevertheless every injection mold is unique and there is an unimaginable number which increases every day.

Or to put it in a different way, imagine yourself in the kitchen, bathroom, office, or sitting in the car. Now imagine all of the plastic parts gone. What remains? Not much is left that is not made of plastic.

In concrete terms: Let's start early in the morning. Before even getting up you hit the alarm button. You already have had the first contact with a plastic part. It continues when you brush your teeth. Today's toothbrushes are, although this is not easily recognizable, manufactured with very complex and complicated injection molds. The conventional toothbrushes with automatically inserted brushes are the simpler version. However, for manufacturing an electrical toothbrush, two different plastics are injected one after another in the injection mold in a very complicated procedure in order to make the rotating brushes in the small brush enclosure.

Hair dryers, coffee machines, tea kettles, refrigerators, stoves, and ovens are just a few consumer goods used in daily life. Opening the door of your car, you again have

contact with plastic parts. Without injection molds, the interior of a car is unimaginable. Seats, steering wheel, switches, buttons, handles, levers, blinds, instruments, covering, trays and so on, a countless number of injection molds are used for the manufacturing of a vehicle.

Plastics surround us in the immediate vicinity of our workplace, whether it is in the workshop, in the office or in school. It doesn't matter what you hold in your hand or use, again it's plastic parts. A computer, a keyboard, whether it is on the machine or on the desk. Everywhere there are things made of plastic, in different colors, contours, shapes, and degrees of hardness—from hard and stable printer housings to the soft and flexible protective covers for the mobile phone.

Last but not least, a child's room! Almost all children's toy boxes are full of toys made from plastic: toy blocks, board game figurines, racetracks, puppets, game consoles, etc. Plastic parts, no matter what we do or where we are, accompany us the whole day. Plastic parts are everywhere, and without them a normal life would be inconceivable.

The list goes on and on. Everyone goes through their day, consciously or unconsciously in contact with plastic parts, but no one thinks about their origin, even though there is a huge worldwide industry behind them. Not only are there manufacturers of injection molds all over the world but also large corporations that manufacture the machines for the production of the plastic parts and very large chemical companies that constantly develop and produce new plastics for different applications. Millions of people are at home in this inconspicuous world.

Through the constant development of ever improving high-quality plastics the application possibilities continue to increase. Sheet metal parts made of steel or aluminum are gradually replaced by plastic parts. Brackets made of metal used for fixing cables, fuel lines, containers, or the like in a car's engine compartment are replaced today by high-strength plastic parts.

Further evidence that this development will certainly continue is the progress in the production of bioplastics. To put it simply, for bioplastics, the petroleum used normally as raw material is replaced by biologically derived material. These oils are extracted from renewable raw materials and are also biodegradable. So far there have only been a few applications that were often only explored by scientific facilities. The whole thing is still in the stages of development. However, if only from the sustainability point of view, bioplastic is predicted to have a bright and important future.

The most significant advantage of plastic parts is that after manufacturing or the injection process a ready-to-use piece comes out of the injection molding machine. The manufacturing time for such a component is only a few seconds. This also has an impact on the much lower cost per piece. But now we come back to the contents of this book—the success of this whole process depends on a high-quality injection mold.

2

Mold Types

■ 2.1 Simple Open/Close Mold

The open/close mold got its name from its easy movement and function when the injection mold for machining of the plastic parts is clamped onto an injection molding machine. The injection mold or the injection molding machine opens and closes without any further necessary movement taking place in the injection mold.

The entire motion sequence is called an injection cycle or just cycle. It begins with a closing of the injection mold. When it is closed, a liquid, hot plastic mass is injected into the injection mold under pressure. Now a certain amount of time must pass before the liquid plastic has cooled and solidified and the plastic part in the injection mold reaches a certain stability. The injection mold opens and the finished, still-warm plastic parts are ejected from the injection mold. When all of the movements are finished, the process starts again. For the outside observer, the machine opens and closes again and again.



In using the term “liquid plastic”, one is referring to plasticized plastic. Plastic pellets are heated and plasticized, which means they become soft and capable of flowing. In this consistency, the plastic can be injected into the injection mold. Depending on the type and kind of plastic pellets, this vary from being highly viscous to having a water-like viscosity.

The direction in which the injection mold or the injection molding machine opens and closes is called the main demolding direction. All movements of the injection molding machine, the injection molds and the moving parts in the injection mold run in this axial direction. Depending on the component there can be additional demolding directions. This is described in Section 2.2.

The open/close mold is the simplest of all injection molds. As a result it is often the cheapest. Already in the planning and designing of plastic parts, efforts are made so that the plastic piece can be produced with this type of injection mold.

Figure 2.1 shows the demolding direction of a simple open/close mold. Both upper part (fixed half) and lower part (moving half) open and close in an axial direction. The plastic part has been designed for being produced with this specific mold in such a way that when opening the mold on the injection molding machine it is not damaged or destroyed.

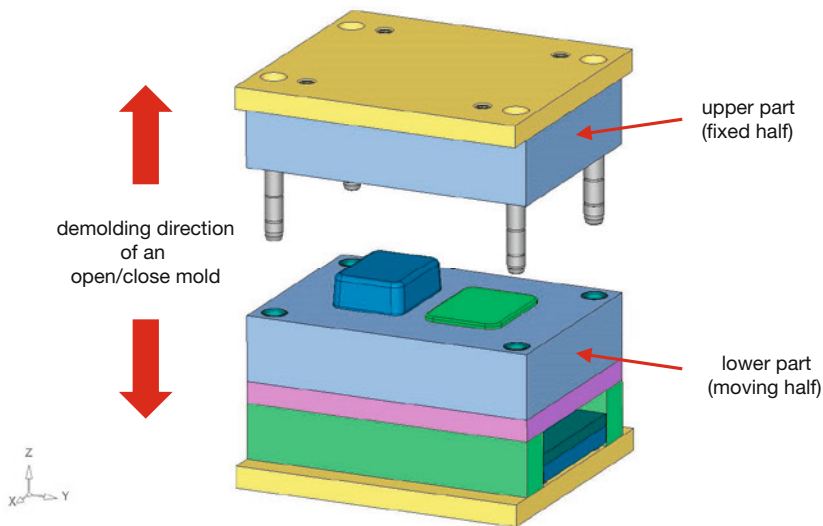


Figure 2.1 Demolding direction

The plastic parts which are to be produced with such an injection mold have no structural elements which deviate from the main demolding direction. Cup-shaped or flat parts, for example, are manufactured with this type of mold.

A plastic part can have elements such as side openings, latches and clips, laterally protruding edges or pipes. For the demolding of these elements, moving components—called slides or inserts—are designed for the mold. In a secondary demolding direction, these elements called undercuts can be removed from the mold without damage. More on this in Section 2.2.

The previously mentioned “expanding” parts container and cover is shown in Figure 2.2 to illustrate how such plastic parts produced in an open/close mold can look.

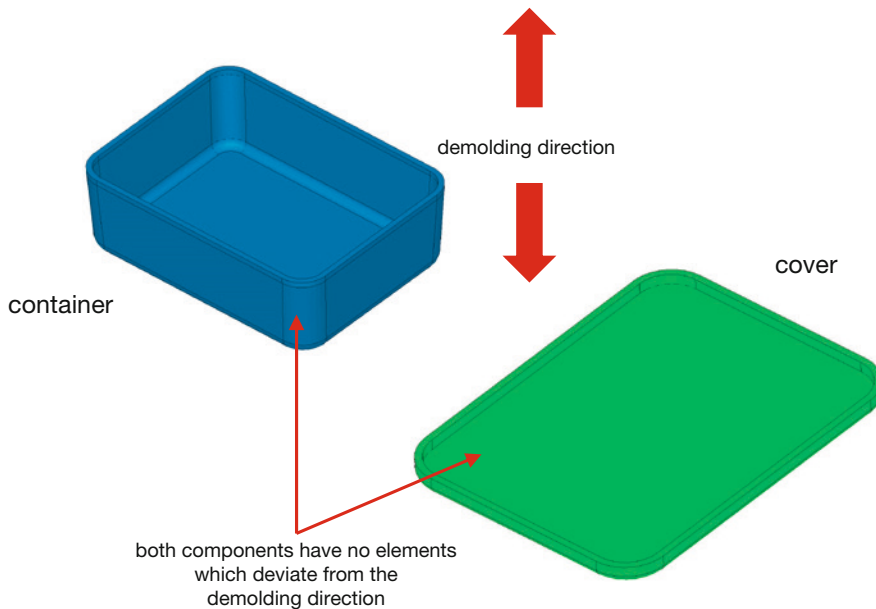


Figure 2.2 Parts for an open/close mold

Here already is the first addition to container and cover. To connect the two and be able to close the container, a sleeve is introduced in every corner of the container and, aligning to the sleeve, a stepped bore is introduced in the cover. Now you can screw down the cover on the container with four screws.

Both the size of the injection mold as well as the open and close technique do not change despite these additions to the plastic parts. The additional elements are also in the demolding direction.

In Figure 2.3, the additional sleeves in the container and the stepped bores in the cover are shown. The demolding direction remains the same.

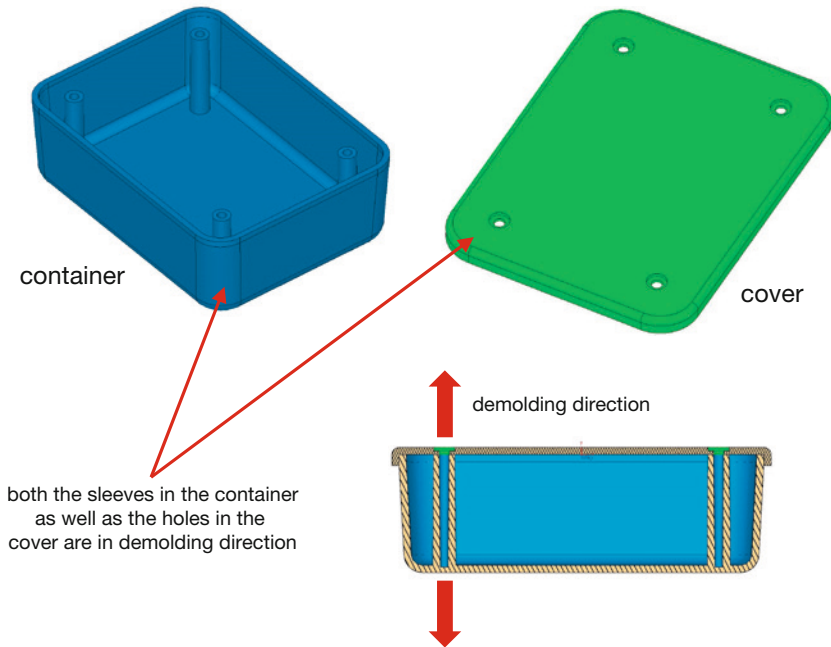


Figure 2.3 Parts for the open/close mold with additional elements

2.1.1 Classic Structure of an Open/Close Mold

The upper part (fixed half) and the lower part (moving half) are made up of several plates and risers. Via the integrated guides, that is, bolts in the fixed half and the bushes in the moving half, the mold closes precisely.

The **fixed half** consists of the clamping plate and the cavity plate. The guide bolts are installed in the cavity plate. The guide bolts are provided at the back end with a collar, which is embedded in the cavity plate. Against the slip out of the guide bolts the clamping plate is screwed tightly with the cavity plate. The cavity plate is fixed to the mold plate via another fitting diameter at the guide bolt.

The **moving half** of a classic open/close mold is made up of the mold plate, possibly a backing plate, the risers and the lower cavity plate. The ejector set is between the risers. The guide bushes are also provided with a collar here and mounted in the cavity plate. They are secured in the moving half through the risers, which are attached, like the fixed half, via the back fitting diameter of the guide bush. The risers are again installed with the clamping plate and with the additional guide sleeves. Everything is screwed tightly together with long screws from the clamping plate through to the mold plate. This guarantees that all components are aligned and tightly connected. Ejectors are the moving parts in the injection mold that

eject or expel the plastic part after opening the mold. Ejectors are usually round pins which are installed in the ejector set. The small rings mentioned at the beginning which are usually visible on the plastic part are the imprints of these ejectors. In Figure 2.4 several longitudinal and cross sections through an injection mold are represented so that the classic structure of an open/close mold can be seen.

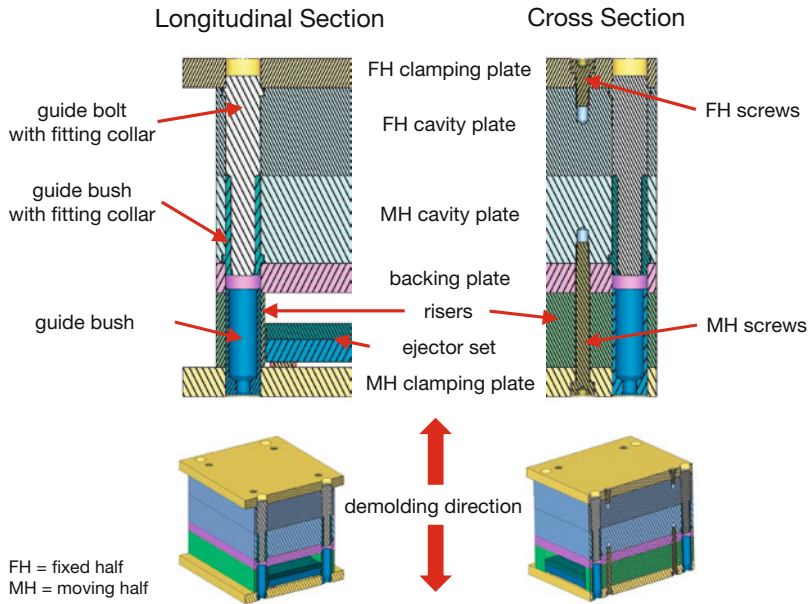


Figure 2.4 Section through a mold structure



The accuracy of fit in a mold is extremely important. Without precise guiding and fixing of both mold halves they can move radially.

2.1.2 Guiding Elements

The guiding elements in an injection mold are very important. They ensure that both mold halves are already centered while closing against each other. Except in special solutions, guide bolts are built into the fixed half and guide bushes are built into the moving half. The tolerances between the cavity plates and the guide bolts and bushes are so small that they are installed with a light press fit.

The fixed half with the guiding bolts fits exactly, free of play, into the guide bushes of the moving half. Only in this way is it guaranteed that both sides fit together on

top of each other precisely and repeatedly. If this were not the case, the mold halves could move radially, which among other things can lead to different wall thicknesses in the plastic parts. This is also called mold offset.

Figure 2.5 shows what can happen when the guiding elements of an injection mold are not exactly aligned.

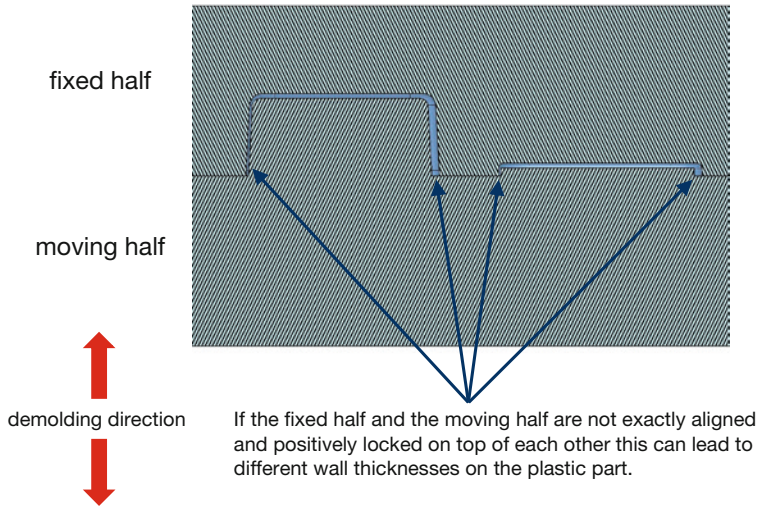


Figure 2.5 Mold offset through insufficient guiding



Here are a few comparisons to get an idea of how important the accuracy of the guiding is. The tolerances between the bolt and the plate have to be so accurate that some light strikes are required when installing the bolt in the plate. If the bolt is just 0.006 mm too thick, it will be very difficult to install.

The tolerance between the guiding bolt and the guiding bush is even smaller. The difference between free-of-play movement and getting jammed is a maximum of 0.004 mm in diameter.

If the center distance between the guiding elements of the plates in the upper part and the lower part differs by more than 0.02 mm it is difficult for the mold to close.

Anti-rotation Protection

Today nearly all injection molds are rectangular. For this reason normally four guiding elements are installed, one in every corner. To prevent a false (rotated) assembly of the fixed half and the moving half, one of the guides is smaller or bigger than the other three.

In Figure 2.6 the fixed half of a mold is displayed: three guide bolts with diameter (\varnothing) 18 mm and one guide bolt with \varnothing 20 mm. This should prevent a false (rotated) assembly of the fixed half on the moving half.

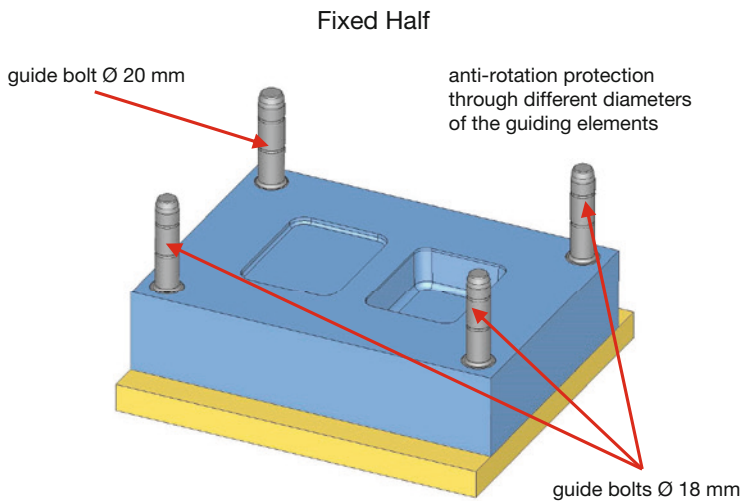


Figure 2.6 Anti-rotation protection in mold making

The following is important for the length selection of the guide bolts: Before the mold contours of the two halves approach, the guides must already fit into one another. If the guides are too short, the mold contour could be damaged during the closing action of the mold halves.

In Figure 2.7 it is clearly visible that the guides are already sliding into one another before both sides can have contact.

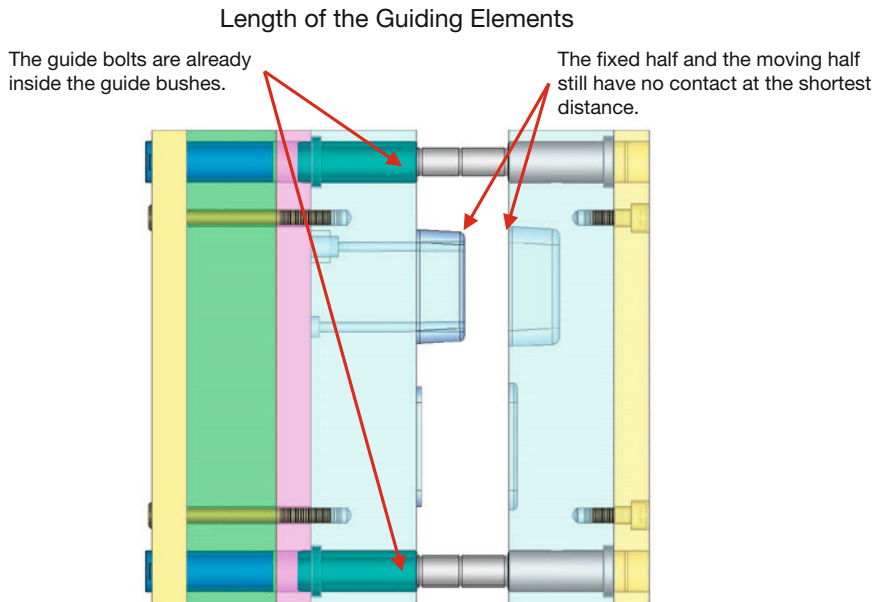


Figure 2.7 Length selection of guiding elements

2.1.3 Backing Plate

These are not used very often in a very simple injection mold. They are installed when a complex cooling, a core pin or additional components that have no space in the cavity plate or pass through the cavity plate and should be held by the backing plate, are required in an injection mold.

In Figure 2.8 a core pin is shown which is installed in the cavity plate and is held by the backing plate.

The use of a backing plate has more functions and advantages here. One of the advantages is that the backing plate is installed under the cavity plate and is level. Therefore all the components which are attached to the backing plate are geometrically determined and on the same level. A further advantage is the manufacturing costs. To achieve a similar fixing of such a core pin, an additional installation of another cover from below would be necessary. A possibility here is a small built-in cover plate or a set screw which fixes the core pin.

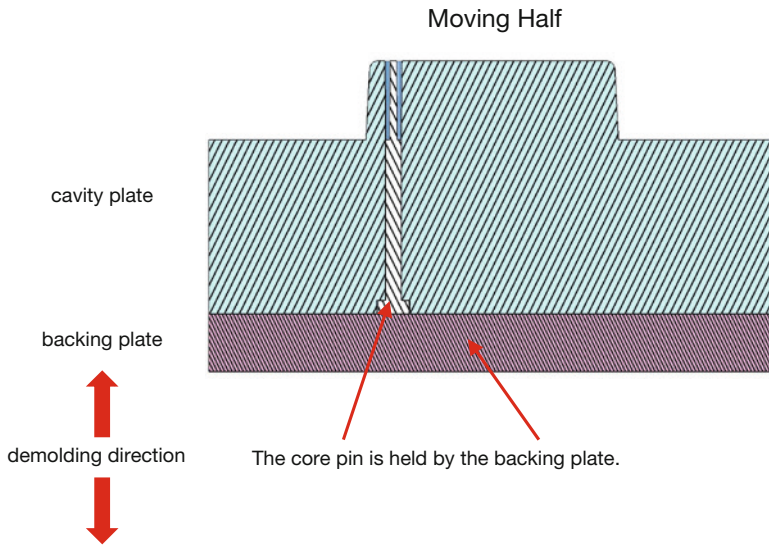


Figure 2.8 The backing plate fixes and holds the core pin

Both alternatives cause higher production costs. If they are used several times in a mold, it makes sense to install a backing plate.

In Figure 2.9 two possible alternatives for the fixing of core pins are shown.

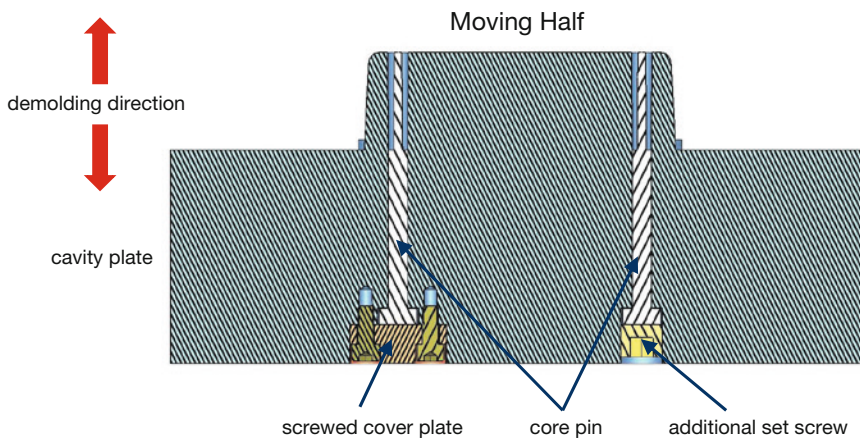


Figure 2.9 Alternatives for fixing

Further additional and basic designs, functions, elements and components of an injection mold are discussed individually in the following sections of this book.

■ 2.2 Molds with Moving Elements

Almost everything that makes an injection mold complicated and expensive originates from the geometry of the subsequent plastic parts. Therefore attention should already be paid in the planning and design of this plastic part that everything that should later contain the plastic part is also to be realized in the injection mold. This is often a big challenge in the development, that is, the design of plastic parts. When design and technology meet, sometimes one has to compromise.

2.2.1 Undercut

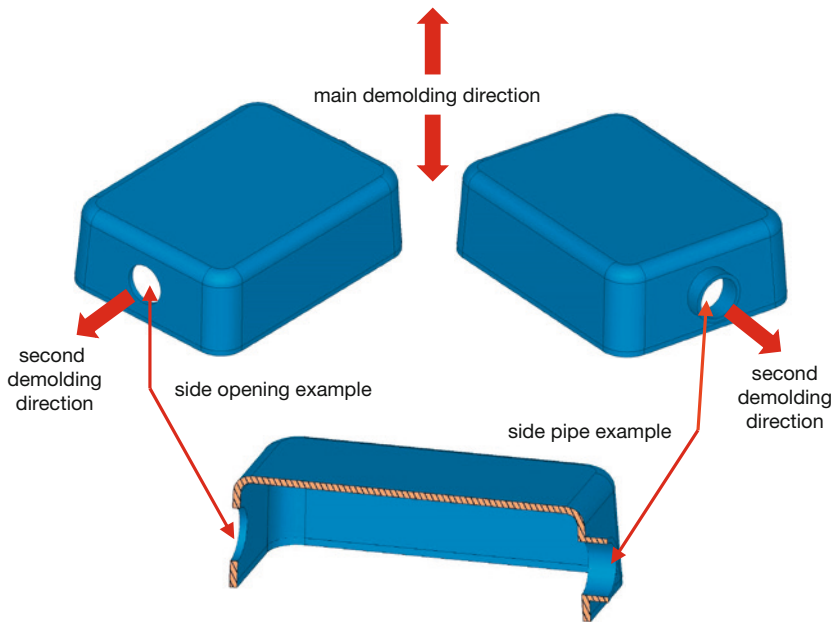


Figure 2.10 Additional demolding directions

The next level of difficulty in plastic parts is elements which cannot be demolded in the main demolding direction like in an open/close mold. These elements, which are troublesome during demolding, are called undercuts. They need to be released or demolded in an additional demolding direction. For this purpose moveable components, such as slides, core pins, ejectors for inclined ejection units or inserts, are used in the injection mold. They support the plastic piece so that it can be better demolded and ejected.

In Figure 2.10 two possible elements, a side bore hole and a side pipe, are seen on our component. Both elements are an undercut on the plastic part and must be released via the second demolding direction. Only this way can the plastic parts be ejected from the mold without damage. For these two examples slides are used to do this.

2.2.2 Slide

When implementing these side openings the open/close mold becomes a mold with slides. Slides are moving components inside the injection mold. One or more parts of the mold contour are incorporated into these slides. The slide itself moves away from the plastic part during or after the opening of the mold in an additional demolding direction. Through this movement the undercuts are released before the plastic part is ejected from the injection mold. The required path is calculated and defined in advance. It must be large enough so that the plastic piece drops out of or can be removed from the injection mold without damage after the ejection.

In Figure 2.11 the slide for demolding the side opening on our container is shown. In the front area of the slide a part of the mold contour of the plastic part is incorporated. The round surface in front has contact with the fixed insert when the mold is closed and is injected. During injection, this contact prevents that the plastic covers this spot and thus forms the bore holes in the plastic part. In technical language, this contact point is also called an aperture.

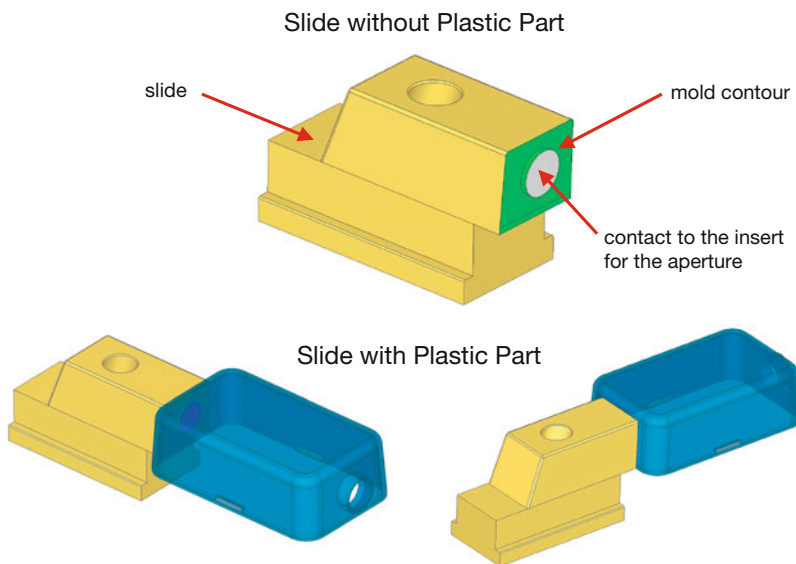


Figure 2.11 Slide with and without plastic part

2.2.3 Slide Operation

To move this slide there are two possibilities. The first possibility is that the slide is connected with a hydraulic cylinder which is in turn screwed tightly to the injection mold. The slide is moved via this cylinder. For this solution the cylinder covers a clearly defined distance. It is bought and installed as a standard part. Find out more in Section 4.2. The second option is the forced control through an inclined pin. The pin is installed with a defined inclination on the fixed half of the injection mold. The front part of the inclined pin submerges in the moving slide. When the mold opens in the main demolding direction, through the resulting movement this inclined pin moves the slide in an additional demolding direction. There are additional details in Section 4.2.

Figure 2.12 displays the closed mold on the left and the slightly open mold on the right. On the slightly open mold the inclined pin has moved the slide in an additional demolding direction to the end position.

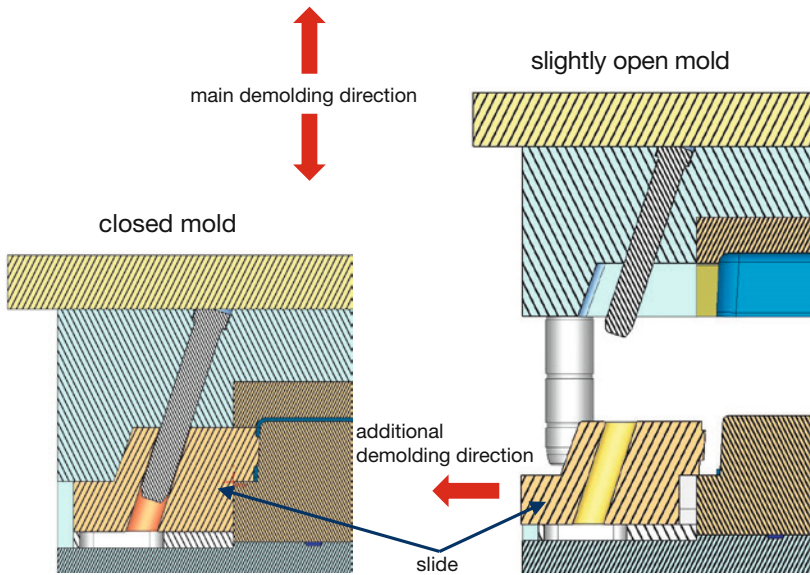


Figure 2.12 Closed and slightly open mold

2.2.4 Latch, Clip Lock

Even a very small and harmless looking clip or catch can have a major impact on the design and on the cost of an injection mold.

The simplest application is a clip for snapping the cover onto the container. Clips or catches are also used to connect several plastic parts or to fix them together in an entire assembly group. The assembly of plastic parts has to be done very fast today and if possible automated. The use of such clip connections on plastic parts has, among others, the advantage that they can be quickly and easily installed without further hand tools.

For the size, type, complexity and also for the costs of an injection mold, it can be very important if the clip is attached outside or inside of the plastic part. This should be considered during the planning of the plastic part. If the clip or latch is outside of the component, it is in the demolding direction and thus there is no undercut. Consequently, it is demoldable without further action.

Figure 2.13 shows both variations of a latch, inside and outside. The outer latch is open above, thus enabling a problem-free demolding. The inner latch is not open in the demolding direction. It will be damaged or even torn away during ejection. Consequently, one must think of how to prevent this.

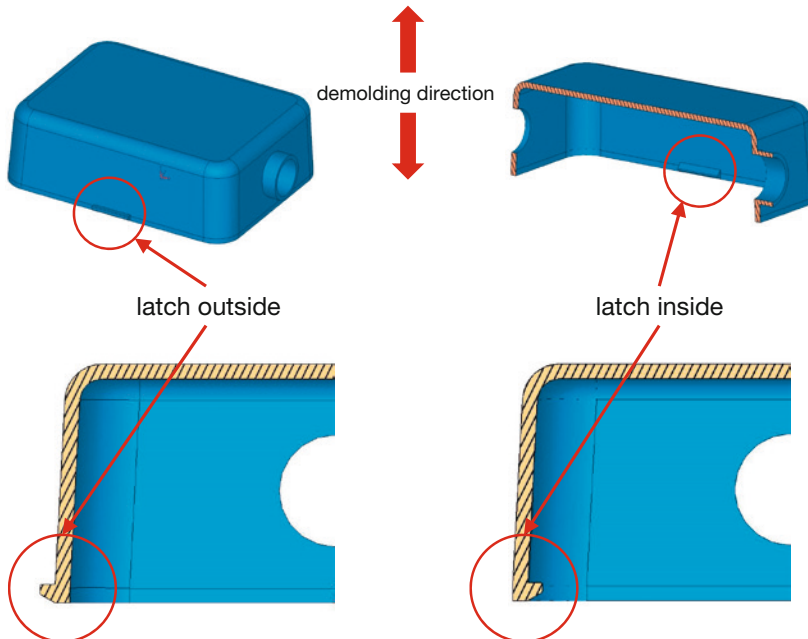


Figure 2.13 Outside and inside latch

Index

Symbols

2.5-axis milling 277
2-C mold 28
2D drawings 43
3+2-axis milling 281
3-axis milling 278
3-C or 4-C mold 29
3D data 43
3D design 43
4-axis milling 279
5-axis machining center 276
5-axis milling 280
5-axis simultaneous hobbing 282
5-axis simultaneous milling 282

A

abrasive plastics 73
adapter nozzle 118
additional centering 94
additional demolding directions 3
additional molding directions 13
air valve 86
aluminum 71
annealing 246
aperture 13
arrangement 70

arrangement of cavities 66
assembly 217, 220
auxiliary ejector 112
auxiliary rib 111

B

backing plate 6, 10
“backpack” slide 167
baffle 189, 193
balancing cavities 260
ball-actuated puller 127
ball catch 162
beryllium copper 146, 197
bioplastics 2
blade ejector 133, 172
blank 29, 200
blockings 147
bore pattern, corrections 144

C

cable 224
CAD
– program 43
– system 43
CAD/CAM system 43, 213
CAD data 284
CAD model 284
CAD system 284

CAM programming 284
catch 162
cavity plate 6
cavity pressure 77
CE certification mark 235
central clamping 67
central ejector 177
change core 144
changes on an injection mold 252
check lists 301
clamping claws 256
clamping plate 6, 33
claws 88
clip lock 15
closing force 67, 77
cloud 45
CNC program 275
coatings 251
cold runner 104
cold runner distributor 105
cold runner distributor cross section 106
cold slug 109
collapsible core 23, 184
color chart 301
complexity of the plastic part 65
confirmation of order 234
connect circuits 198
connection 69

connectors of components 224
 constrained shrinkage 53
 continuous production 73
 contour changes 143
 contoured ejector 175
 contour-forming split line
 face 90
 controlled needle 120
 converting 45
 cool core 143
 cooling 140, 188
 – check for leaks 227
 cooling circuits 188
 cooling circuits, redirect 192
 cooling connectors 226
 cooling hole, sealing 141
 cooling in slide 163
 cooling system 185
 cooling time 262
 copper 205, 289
 copper alloy 143
 copper cores 197
 core pins 10, 12
 – fixing 11
 core pullers 256
 corner warping 59
 costs 15, 18, 65, 117, 119
 – determine 253
 cotter 76
 cotter surface 160
 cup-shaped plastic parts 4
 cycle 30
 cycle determined 70
 cycle time 262
 cylinders 155

D

data
 – amount 44
 data size 43, 47
 data transfer 44

date stamp 202
 dead-end recess 110
 dead spots 118
 deep hole drills 294
 deflection elements 198
 delay 166
 demolding 12, 80
 demolding direction 4, 61
 – additional 3, 13
 – main 3, 12, 169
 – second 13
 – secondary 4
 demolding problems 85
 design 43
 design discussion 235
 design elements 43
 de-spindling 23, 24
 diaphragm gate 114
 dielectric 288
 DIN 912 138
 DIN 16742 53
 DIN 66217 277, 279
 direct injection 68
 displaced air 129
 distributor 118
 dome 62, 81
 dosing 259
 draft angle in the split 83
 draft angles 80
 drilled cooling 190
 drilling 293
 durability 137
 DXF 45

E

economic calculation 65, 119
 edge length 19
 EDM 87, 205
 EDM scale 94
 ejection unit 257
 ejector as tool 176

ejector base plate 170
 ejector bolts 255
 ejector cover plate 170
 ejector for inclined surface 12
 ejector guiding 128
 ejector imprints 85
 ejector pins with ball heads 126
 ejectors 16, 62, 85, 169
 ejector set 6, 16, 170
 electrode 205
 end position 14, 94, 161
 end-position locking 162
 end-position locking security 159, 179
 energy efficiency 257
 engineer's blue 222
 entrapped air 97
 error quota 239
 etched pattern 94
 etching process 207
 external thread 19, 20

F

feeder 37
 feed point 95, 130
 feed point location 96
 fiber glass 49
 fillers 49
 filling simulation 97
 filling study 122, 259
 film gate 113
 final assembly 236
 finishing processing 282
 finish milling 281
 fit 219
 – accuracy 242
 fits 241
 fitting 199
 fixed half 4, 6
 fixing of core pins 11
 flat plastic parts 4
 flow line 97, 121

forced control 14, 21, 155
 forced demolding 17, 185
 forced removal 17
 forces in mold 265
 formulas and calculations 302
 free shrinkage 53
 ftp server 45

G

gate. *See* feed point
 gear 35, 39
 gear rack 23, 25, 28
 gear wheel 25, 26
 glass beads 49
 graining 207
 graphite 205, 289
 grease 154
 grease pockets 154
 grinding 292
 guide bushes 6
 guide nut 25, 26
 guides 7
 guide shoe 38, 40
 guide thread 25
 guiding 153
 guiding bolts 7
 guiding bolts, length selection 9
 guiding in injection mold 153

H

hard components 30
 hardening 137, 247
 hard-soft 29
 heat exchange 186
 heating cartridges 198
 heat pipes 196
 heat treatment 245
 – types 246
 high-helix lead screw 23, 26, 28

high-helix nut 26
 high-helix thread drive 27
 holding pressure 49, 57, 258
 hoses 224
 hot runner 37, 104
 hot runner distribution system with needle valve 120
 hot runner distributor 118
 hot runner single nozzle 116
 hot runner with needle valve 32
 hydraulic connectors 226
 hydraulic cylinder 14, 25, 158, 167
 hydraulic unscrewing unit 24

I

IGES 45
 impact wall 110
 inclined contour ejectors 219
 inclined ejector 16, 169, 175, 178
 inclined pin 14, 21, 155, 166
 inclined pin/cotter surface relationship 157
 inclined pin, mechanical 156
 initial sample 267
 initial sample inspection report 237
 initial sample report 266
 injection burr 260
 injection cycle 3
 injection mould 1
 injection moulding machine 1
 injection pressure 49, 77
 inserts 12, 137
 installation 215

 – from inside to outside 215
 installation height 255
 installation height, higher 42
 integral hinge 121, 124
 integral joint 124
 internal mold pressure 265
 internal thread 19, 23

J

jet 110
 jumping split line face 90

L

label on mold 267
 laser beam welding 271
 LaserCUSING 296
 laser sintering 296
 laser texture 208
 latch 15
 leachate 73
 lifting bridge 256
 limit switch 224
 locating ring 255
 locks 94, 266
 longitudinal direction 52
 loose fits 241
 lubrication 154

M

machine base 38, 40
 machine size 65, 75
 machine sprue bush 37
 main demolding direction 3, 83, 169
 maintenance
 – ongoing 269
 – predictive 270

maintenance schedule
 269, 302
 male connector 224
 manifold 118
 manufactured parts 214
 manufacturing costs 10
 manufacturing
 technologies 275
 marking 201
 marking type 202
 material accumulation 70
 material pairings 29
 material selection 48
 material selection for
 injection mold 71
 measuring pressure 227
 melting temperature 118
 melt temperature 263
 microstructure, changes
 246
 milestone 236
 milled profile 87
 milled structure 204
 milling 87, 275
 milling direction 87
 milling head 281
 milling machine 277
 milling paths 286
 mirror polishing 299
 mission statement 239
 mold contour 13, 149
 mold core in slides 148
 mold cores 23, 142
 mold documentation
 235
 mold for thread 19
 mold halves 8
 molding shrinkage 50
 mold insert
 – divide 137
 – edge 139
 mold inserts 137
 mold locking device 256
 mold offset 8
 mold plan 257

mold related dimensions
 53
 mold size 18, 19, 75
 mold split 89
 mold temperature 49, 98,
 263
 mold types 3
 mold with moveable
 elements 12, 23
 mold with rotary plate 32
 mold with slides 13
 motion sequence 3, 40,
 257
 moveable components 12
 moving half 4, 6
 multi-cavity mold 28, 69
 multi-component injection
 molds 28, 35

N

NC data 43
 neutral data format 44
 nitriding 249
 non-mold related
 dimensions 53
 nozzle radius 255
 number of cavities 64,
 75

O

oblong hole 166
 offset split 94
 open/close mold 3
 opening and closing 38
 optimizing of parameters
 262
 order 234
 O-ring seal 140, 218, 228
 output quality 64, 66, 71
 over injection 67

P

parameter 257
 pilot drill 294
 plastic granulates 1
 plastic parts 1
 plastic suitable design 61,
 80
 plate thickness 79
 pocket bottom 218
 polishing 87, 209, 298
 post processor 287
 post shrinkage 50
 practical guidelines 301
 precision 94, 241
 press fits 241
 process chain 231
 procurement process
 233
 production costs 11
 production cycle, typical
 258
 profile grinding 293
 projected surface 160
 pulling ejector 169
 push back pin 176
 push-in connection 199
 pushing ejector 170

Q

quality assurance 239
 quick connect couplers
 199, 226

R

ramp 151, 242
 recycling 96
 release 238
 repairs 272
 replacement parts 270
 residual cooling time 264
 resulting movement 14,
 16

ribs 62, 81, 133
 right hand principle 279
 ring gate 115
 risers 6
 rotary plate 33
 rotary table technology 32
 roughing 281
 rough surface 204
 runner 69, 97, 105, 126

S

sample mold 71, 137
 screw 258
 screw cap 20
 screw coupling 20
 screwed-in core 146
 screwing movement 23, 24
 screws 6
 seal 33
 sealing plug 199
 sealing point 259
 sealing slide 35
 self-locking effect 138
 semi-finished parts 33
 sequential function chart 301
 serial mold 137
 server 45
 service life 71
 set screw 10
 shear forces 147
 shifting technology 29
 shrinkage 48, 61, 97
 side opening 13
 silicone 50
 simulation 56, 96, 97
 simulation program 56
 sinker EDM 289
 sink marks 146
 sleeve ejector 131, 173
 slide 12, 21, 76, 91, 146
 – split line 150

slide body 153
 slide design 148
 slide guide 22, 220
 slide in slide 165
 slide lock technology 35
 slide operation 14, 155
 slide width 155
 sliding guides 38
 smallest draft angle 81
 soft components 29, 34
 soft material 29
 spacing rollers 80
 specifications 60
 spindle drive 27
 spiral core 195
 split 89, 222
 split edges on insert 93
 split line
 – visible 94
 split line face
 – contour-forming 90
 – jumping 90
 – plain 89
 split line faces, two 35
 split line on slide 150
 split line surface 22
 spotting 222
 spotting edge 223
 spring ejector 175
 spring in slide 161
 sprue 67, 69, 96
 sprue ejector 177
 sprue length 128
 sprue line 96
 sprue on the part 107
 sprue picker 96, 125
 sprue system 103
 sprue type 103
 stack mold 35, 65
 stainless steel 74
 standard parts 213
 standards 240
 STEP 44, 46
 STL 46
 stress whitening 85

stripper plate 180, 185
 surface 63, 87, 94, 203
 surface grinding 293
 surface modelling software 45

T

talc 49
 technical specification 235
 temperature balance 117, 119, 185, 263
 temperature balance of the mold 49
 temperature of the liquid plastic 49
 tempering temperature 247
 T-guiding 153
 thermal sensor 224
 thread halves 20
 three plate mold 125
 TIG welding 270
 tilting rotary table 283
 TiN coating 251
 toggle lever 40
 tolerances 7, 53
 transfer point 37
 transport bridge 225
 transverse direction 52
 transverse hole 140
 triangular facets 47
 tunnel gate 96, 108
 tunnel gate inserts 128
 tunnel in the fixed half 108, 109
 turning 295
 two-component injection mold 28
 two-stage ejector 181
 two units 30

U

undercut 12, 16, 20
unscrewing movement 23
unscrewing unit 28
USB memory stick 238
USB stick 45

V

vacuum 82, 86, 88, 139
vacuum hardening 247
vacuum soldering 297
validation 231, 255

VDI 3400 205, 289
ventilation 129, 139, 150, 176, 263
ventilation channel 132
ventilation insert 134
ventilation in the split 135
ventilation on ejector 135
ventilation via components 132
Vickers hardness 250
visible face 63
visible split line 94
vision 239
visual inspection 227
volumetric filling 259

W

wall thickness 8, 49, 58
warping 56, 97
wear 272
wear plates 92, 222
welding 270
weld penetration 270
whip gate 128
wire EDM 288, 291
without damage 62
wrong side 87